

# INFLUENCE OF MILLING TIME ON STRUCTURAL AND MAGNETIC PROPERTIES OF ZnO NANOPARTICLES PREPARED BY MECHANICAL MILLING

*by* Kontan Tarigan

---

**Submission date:** 07-Apr-2019 02:25PM (UTC+0700)

**Submission ID:** 1107313530

**File name:** 2010-JFis-2-ZnO.pdf (785.86K)

**Word count:** 4677

**Character count:** 27690

ISSN 0854-3046  
Akreditasi Nomor: 242/Akred-LIPI/P2MBI/05/2010

---

**JURNAL FISIKA**  
**Himpunan Fisika Indonesia**

---

**Volume 10 – Nomor 2 – Desember 2010**



**Diterbitkan oleh**  
**Himpunan Fisika Indonesia**

## JURNAL FISIKA HIMPUNAN FISIKA INDONESIA

### DEWAN EDITOR :

50 Prof. Dr. Masno Ginting, M.Sc. (Pusat Penelitian Fisika - Lembaga Ilmu Pengetahuan Indonesia)  
60 Prof. Dr. Masbah Rotuanta Tagore Siregar (Pusat Penelitian Fisika - Lembaga Ilmu Pengetahuan Indonesia)  
Prof. Dr. Pramudita Anggrai (Badan Tenaga Nuklir Nasional, Jogjakarta)  
Dr. Bambang Widiyatmoko, M.Eng. (Pusat Penelitian Fisika - Lembaga Ilmu Pengetahuan Indonesia)  
Dr. Euis Sustini, MS (Institut Teknologi Bandung, Bandung)

### MITRA BESTARI:

Prof. Suhk Kun Oh (Chungbuk National University, Korea)  
Prof. Jean Soo Chung (Chungbuk National University, Korea)  
Prof. Ching Ray Chang (National Taiwan University, Taiwan)  
Prof. Surian Pinem, M.Si. (Badan Tenaga Nuklir Nasional, Serpong)  
Dr. Ir. Sekartedjo, M.Sc. (Institut Teknologi Sepuluh Nopember, Surabaya)  
Prof. Dr-Ing. Mitra Djamal, M.Sc. (Institut Teknologi Bandung, Bandung)  
Dr. Ir. Harry Arjadi, M.Sc. (Pusat Penelitian Sistem Mutu dan Teknologi Pengujian - Lembaga Ilmu Pengetahuan Indonesia)  
Dr. Tech. Djok Riyono (Universitas Indonesia, Depok)  
Dr. Darminto, M.Sc. (Institut Teknologi Sepuluh Nopember, Surabaya)  
Dr. Buldan Muslim, M.Si. (Lembaga Penerbangan dan Antariksa Nasional, Bandung)

### EDITOR PELAKSANA :

16 Dra. Dwi Bayuwati, M.Eng.Sc. (Pusat Penelitian Fisika - Lembaga Ilmu Pengetahuan Indonesia)  
Zainal Akbar, S.Kom., M.Eng. (Pusat Penelitian Fisika - Lembaga Ilmu Pengetahuan Indonesia)  
Syuhada, S.Si., MSc. (Pusat Penelitian Fisika - Lembaga Ilmu Pengetahuan Indonesia)

## HIMPUNAN FISIKA INDONESIA

### Anggota Kehormatan:

Prof. Claude Cohen Tannoudji (1997 Noble Prize Winner, Ecole Normale Supérieure, French)  
Prof. Emeritus Anthony Philip French (Massachusetts Institute of Technology, USA)

**Ketua :** Prof. Dr. Masno Ginting, MSc.  
**Sekretaris:** Dra. Edi Tri Astuti, M. Eng.

**Wakil Ketua :** Prof. Dr. Pramudita Anggraita  
**Bendahara :** Dr. Maria Margaretha Suliyan

### Alamat Sekretariat :

28 Komplek Batan Indah Blok L No. 48 Serpong,  
Tangerang 15314, Banten, Indonesia  
Tlp/Fax: 62 - 21- 756 1609  
Webmail: <http://hfi.fisika.net>,  
Email : [info@hfi.fisika.net](mailto:info@hfi.fisika.net), [jurnal@hfi.fisika.net](mailto:jurnal@hfi.fisika.net)

5 Pusat Penelitian Fisika-LIPI, Kawasan Puspiptek  
Serpong , Tangerang 15314, Banten, Indonesia  
Tlp : 62 - 21- 756 0556, 756 0570  
Fax : 62 - 21 756 0554  
Webmail: <http://hfi.fisika.net>,  
Email : [info@hfi.fisika.net](mailto:info@hfi.fisika.net), [jurnal@hfi.fisika.net](mailto:jurnal@hfi.fisika.net)

## INFLUENCE OF MILLING TIME ON STRUCTURAL AND MAGNETIC PROPERTIES OF ZnO NANOPARTICLES PREPARED BY MECHANICAL MILLING

K. Tarigan<sup>1,2</sup>, M. Ginting<sup>3</sup>, V. D. Lam<sup>4</sup>, T. D. Thanh<sup>4</sup>, D. H. Manh<sup>4</sup>, T. L. Phan<sup>1</sup>

<sup>1</sup>Department of Physics, Chungbuk National University, Cheongju 361-763, Korea

<sup>2</sup>Department of Electrical Engineering, Indonesia Institute of Technology, Serpong,  
Tangerang Selatan 15320, Indonesia

<sup>3</sup>Research and Development Center for Applied Physics, LIPI, Serpong,  
Tangerang Selatan 15314, Indonesia

<sup>4</sup>Institute of Materials Science, Vietnam Academy of Science and Technology, Hanoi, Vietnam  
E-mail: ptlong2512@yahoo.com

### ABSTRACT

Influences of the milling time on structural and magnetic properties of nanocrystalline ZnO samples prepared by mechanical milling process have been studied in detail. Experimental results reveal that with varying the milling time from 1 to 24 hrs the average crystallite size calculated from Scherrer's equation is in the range of 13 - 18 nm. All the samples exhibit the ferromagnetic behavior above room temperature. The ferromagnetic order increased with increasing the milling time. By means of X-ray diffraction analyses and measurements of the magnetization versus temperature, we suggest that the ferromagnetism in ZnO nanoparticles is due to a  $\text{Fe}_{0.902}\text{O}$ -related metastable phase, in which Fe impurity is generated from the stainless steel vial wall and balls.

**Keywords:** ZnO nanoparticles; mechanical milling; X-ray diffraction; magnetism.

### ABSTRAK

Pengaruh waktu milling terhadap sifat-sifat struktural dan magnetik sampel nanokristalin ZnO yang dibuat dengan proses milling mekanik telah dipelajari secara rinci. Hasil-hasil eksperimen memperlihatkan, dengan perubahan waktu milling dari 1 ke 24 jam menghasilkan ukuran rata-rata kristalit yang dihitung dengan persamaan Scherrer adalah antara 13 - 18 nm. Semua sampel menunjukkan perilaku feromagnetik di atas suhu kamar. Sifat feromagnetik meningkat mengikuti pertambahan waktu milling. Berdasarkan hasil analisa difraksi sinar-x dan peralatan magnetisasi versus temperature, kami menduga bahwa sifat feromagnetik dalam nanopartikel ZnO ini berhubungan dengan fase metastabil  $\text{Fe}_{0.902}\text{O}$ , di mana impuritas Fe dihasilkan dari dinding stainless steel vial dan bola-bola.

**Kata kunci:** ZnO nanoparticles; mechanical milling; X-ray Diffraction; magnetism.

PACS: 81.05.Dz, 61.46.Hk, 75.75.-c

## INTRODUCTION

Zinc oxide (ZnO) is an inexpensive and highly chemical- and thermal-stable semiconductor compound. It is emerging as a potential material for a variety of applications. In electronic and optoelectronic fields, conductive and transparent natures make ZnO suitable for displays and photovoltaic panels, which can replace for another costly transparent conductor of ITO. With a wide-band gap (3.37 eV) and a large exciton binding energy (60 meV), ZnO is considered as an important material for ultraviolet/blue devices working at room temperature. It has been also used the piezoelectric property of ZnO in some commercial products such as accelerometers, force sensors, pressure sensors, acoustic sensors, and ultrasonic transducers [1, 2]. Particularly, with biocompatibility and no-toxicity it is suitable for personal care applications of sunscreen products, cosmetics (due to ZnO's preeminent behavior in absorbing ultraviolet radiations), and medical creams.

Recently, it has been discovered that ZnO exhibits a variety of novel structures in the nanoscale, including nanoparticles, nanowires, nanotubes, nanocombs, and so forth [2, 3]. This opens up new potential applications in nanoscale electronic and optoelectronic devices [2-8], and biomedical and environmental technologies [9-11]. For example, ZnO nanowires/nanorods can be used in nanogenerators [5, 6] and gas sensors [4]. With the successful growth of *p*-type ZnO nanowires/nanorods, it is expected to fabricate a new generation of inexpensive ZnO-based light-emitting diodes (LEDs) [7, 8]. Concerning ZnO nanoparticles, their applications are widely in many fields, including phosphor powders, photocatalysis, textiles, food additives, pigments, and microorganism [2, 9, 11, 12]. Thus, the fabrication of a large amount of ZnO nanoparticles is always an imperative demand.

Basically, there are two approaches of "bottom-up" and "top-down" to synthesize ZnO nanoparticles. While the former is based on advanced chemical methods (such as the sol-gel technique, aqueous chemical deposition, chemical co-precipitation, *etc.*), the latter is based on the high-energy ball milling (mechanical grinding process) with low-cost production [13]. The starting materials for the mechanical milling are usually micro-sized powders. In the ball-milling operation, there are two processes taking place simultaneously: particle fracturing and cold welding. The powders are plastically deformed under high-energy impacts through ball-to-ball and ball-to-vial wall collisions. The grinding process thus depends on many factors, including temperature, ambient, chemical composition of powder mixtures, grinding tools, and so forth [13, 14].

Because of the capacity in fabricating a large amount of nanoparticles, this method has been used to make ZnO nanoparticles [15-21] as starting from commercial ZnO powders. To fabricate ZnO nanoparticles, milling tools (balls and vials) of zirconium, agate, and stainless-steel are employed. The use of such the milling media, synthesized ZnO nanoparticles are usually adhered by impurities



generated from balls and vials [17, 20]. However, this situation has not been investigated in detail yet, particularly for ZnO nanoparticles fabricated in the stainless-steel milling medium.

In this work, we report a thorough study of the influences of the milling on the structural and magnetic properties of nanocrystalline ZnO samples prepared by high-energy ball milling in which the stainless-steel vial and balls are used. Our experimental results have proved an existence of a secondary phase generated from the milling medium, which is responsible for ferromagnetism in the samples.

## EXPERIMENTAL DETAILS

To make nanoparticles, we used commercial ZnO powders (99.995% purity, and particle diameters of about 200 nm) as the precursor. For each sample, an amount of 3.5 g ZnO powders was loaded in a stainless-steel vial containing five balls (two balls with 10.7 mm diameter, and the others with 4.5 mm diameter). The ball-to-powder ratio was 5:1. Before milling process, we carried out the coating step for 30 minutes to avoid impurity from vial and balls. The milling process was performed at room temperature by 8000D Dual Mixer/Mill (SPEX Sample Prep) in an Ar ambient to avoid air contamination. The milling time ( $t_m$ ) was varied to be 1, 3, 9, 12, and 24 hrs. This process is shown in Figure 1. For reference, powders clung to the vial wall and balls were scraped to check their properties (this sample was named R). The morphology and particle size of the final samples were examined by a field-emission electron scanning microscope (FE-SEM, Hitachi S-4800). Energy dispersive X-ray (EDX) spectroscopy link with FE-SEM was used to identify impurities present in the samples. The crystal structure was analyzed by an X'Pert Philips diffractometer. The x-ray radiation source was Cu- $K\alpha_1$  ( $\lambda = 1.5406 \text{ \AA}$ ), at applied voltage and current of 40 kV and 30 mA, respectively. Magnetic measurements at room temperature were performed on a superconducting quantum interference device (SQUID), and measurements at high temperatures (above 300 K) were carried out on a vibrating sample magnetometer (VSM).


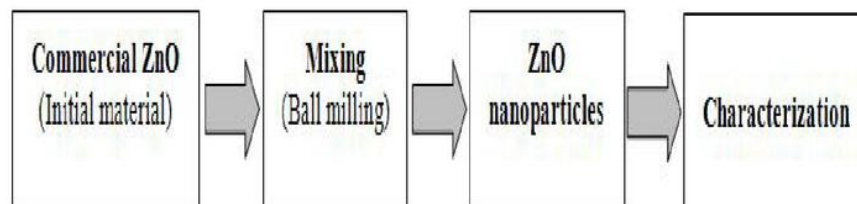


Figure 1. Diagram shows preparation of ZnO nanoparticles.


## 44 RESULTS AND DISCUSSION

Figure 2 shows SEM images of four representative ZnO samples with various milling times of 1, 3, 9, and 24 hrs. One can see that the morphology and size of particles are changed very much when the milling time ( $t_m$ ) is increased. This is due to the impaction of high energy generated from the ball-to-ball and ball-to-vial wall collisions. For the  $t_m = 1$  hr sample, particle sizes are various in the range of 50 to 200 nm. The  $t_m$  increase longer than 9 hrs introduces particles with more homogeneous sizes of about 20 nm. However, these nanoparticles adhere to each other to form clusters with dimensions of 50 - 100 nm, see Figs. 2(c and d). Having used EDX spectroscopy linked with SEM, we find Fe impurity present in the nanocrystalline ZnO samples, see Figure 3.


This impurity is generated from the stainless steel balls and vial wall. Its concentration increases with increasing  $t_m$ , and is estimated to be about 0.4 - 1.2 wt%. For a longer milling time of  $t_m = 100$  hrs, Glushenkov *et al.* [17] also found their nanocrystalline ZnO samples containing 6.7 wt% Fe and 1.3 wt% Cr. The absence of Cr impurity in our samples could be due to the fact that the milling time is short or its concentration is too low, which is not detected by EDX spectroscopy.

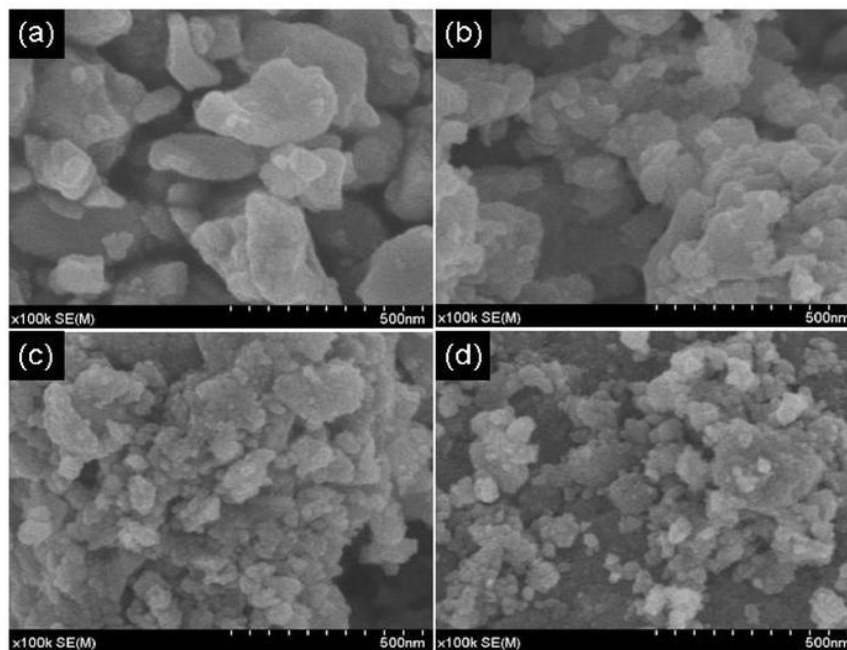

9  
26  
**Figure 2.** FE-SEM images for ZnO nanoparticle samples with the milling times of (a) 1 hr, (b) 3 hrs, (c) 9 hrs, and (d) 24 hrs.

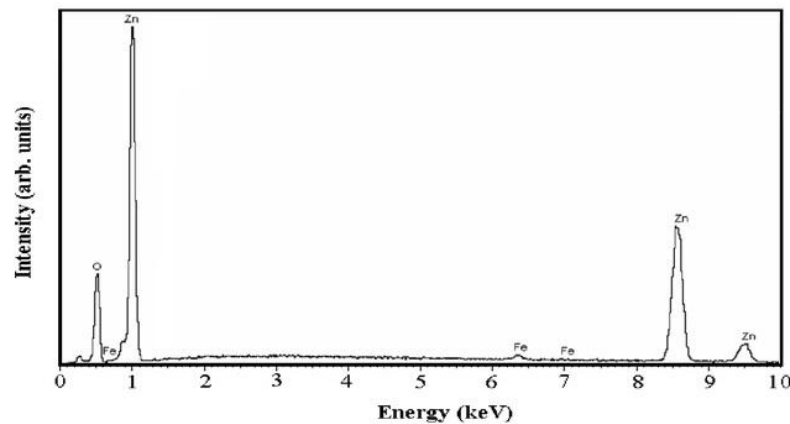

**Figure 3.** EDX spectrum for the sample with  $t_m = 12$  hrs showing the presence of Fe impurity besides Zn and O.

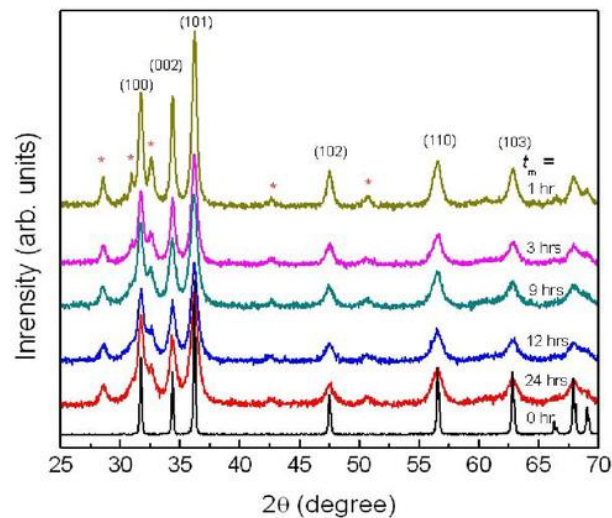

**Figure 4.** XRD patterns for the nanocrystalline ZnO samples with various milling times in comparison to the as-received ZnO powders (0 hr). Asterisks shows a  $\text{Fe}_{0.902}\text{O}$ -related secondary.

To examine structural characterization, we have based on an x-ray diffractometer. **Figure 4** shows x-ray diffraction (XRD) patterns of the samples with various milling times. Having compared to the as-received ZnO sample ( $t_m = 0$  hr) corresponding with the indexed XRD peaks, one can see that there is no shift of peak positions for the milled powders. This reflects that the nanocrystalline samples are stable in the wurtzite-type structure. The lattice parameters determined are  $a = 3.26$  and  $c = 5.22$  Å,



and seem independent of  $t_m$ . The  $t_m$  increase only causes the weakening and broadening of the diffraction peaks, indicating a disordered crystalline structure and small grain size. In fact, ZnO is a brittle material.


During milling, the local heating effect appearing at contact points of the ball-to-ball and ball-to-vial wall causes plastic deformation of ZnO powders. The decrease in grain/crystallite size is hence completely possible. In an attempt to obtain the crystallite size ( $D$ ), we used the Scherrer formula [22]:

$$D = \frac{K\lambda}{\beta \cos \theta}, \quad (1)$$


where  $\beta$  is the FWHM,  $K$  is a constant ( $= 0.89$ ),  $\lambda$  is the x-ray wavelength, and  $\theta$  is the Bragg angle. For each sample we calculated  $D$  for all the indexed peaks, and then took their average value. The results obtained are shown in Figure 5. It appears that  $D$  slightly decreases from about 18.5 nm for the  $t_m = 1$  hr sample to 13.5 nm for the  $t_m = 12$  hrs sample. In our case, the value with  $D = 13.5$  nm is considered as a critical size that the  $t_m$  increase up to 24 hrs does not further reduce  $D$ . Such the tendency is in good agreement with SEM data shown in Figure 2. It is different from previous works that employed a similar milling medium [17, 18], the XRD patterns of our samples exhibit extra peaks besides the main peaks from the wurtzite ZnO, see asterisks in Figure 4. These extra peaks match well with those of the  $\text{Fe}_{0.902}\text{O}$ -wuestite structure (the space group:  $Pm\bar{3}m$ ). Here, Fe impurity is generated from the stainless steel vial wall and balls. Under high energy of the milling operation together with the presence of oxygen in the vial, the  $\text{Fe}_{0.902}\text{O}$  phase is constituted. Its XRD peaks are also widened as increasing  $t_m$ , revealing that  $\text{Fe}_{0.902}\text{O}$  is in nano-size. However, a question about the position of this phase in the samples (*i.e.*, it coated on ZnO nanoparticles and/or distributed as separate particles) is still a challenge, which warrants further study.

Following structural investigations, we have studied magnetic properties. Figure 6 shows the field dependences of magnetization ( $M$ - $H$ ) for the samples with various milling times and for sample R. The sample denoted R is powders clung to the vial wall and balls, see the experimental part. These data were recorded at 300 K by SQUID. All the samples exhibit the ferromagnetic behavior. Among these, sample R (is nanoparticles scraped from the balls and vial wall) has the greatest magnetization.

Meanwhile, for the others the ferromagnetic order increases with increasing  $t_m$ . Particularly, the  $M$ - $H$  curves attain to saturation values at applied fields beyond  $\pm 3$  kOe. From these data, we determined values of the saturation magnetization  $M_s$  and the coercivity  $H_c$  with respect to  $t_m$ , as graphed in Figure 7. Both  $M_s$  and  $H_c$  increase gradually when  $t_m$  is increased from 1 to 24 hrs.

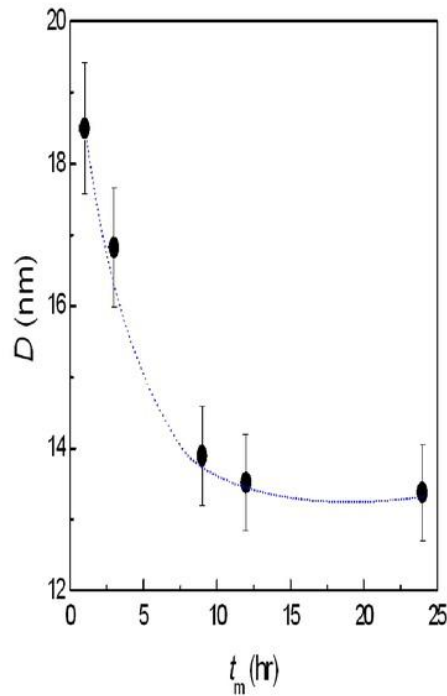


**Figure 5.** The  $t_m$  dependence of the average crystallite size ( $D$ ) for nanocrystalline ZnO samples. The dotted line is to guide the eye only. Error bars of 5 % are shown.

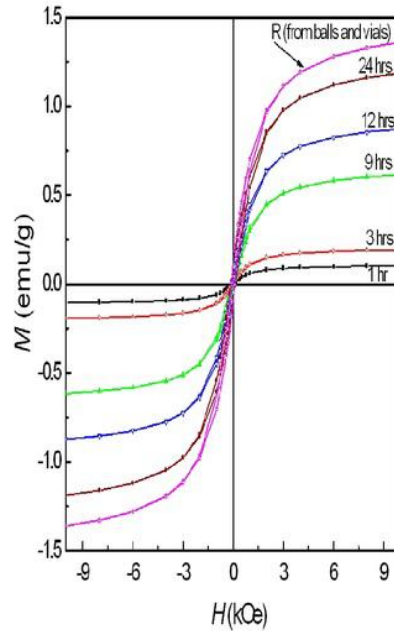


**Figure 6.** Hysteresis loops for the nanocrystalline ZnO samples with various milling times recorded at 300 K.

For the  $t_m = 24$  hrs sample,  $M_s$  and  $H_c$  values are about 0.96 emu/g and 120 Oe, respectively. These values are much greater than those determined from other ZnO-based materials, as reviewed in Chapter 5 of Ref. [23].

To gain more insight into the magnetic properties of the system, we have chosen two representative samples of R and  $t_m = 12$  hrs for magnetic measurements at temperatures above 300 K by using VSM. Notice that during the measurement, the samples are put in an Ar ambient to avoid contamination from air. Figure 8 shows temperature dependences of magnetization ( $M$ - $T$ ) for these samples, which were measured under heating and cooling conditions named MT1 and MT2, respectively.

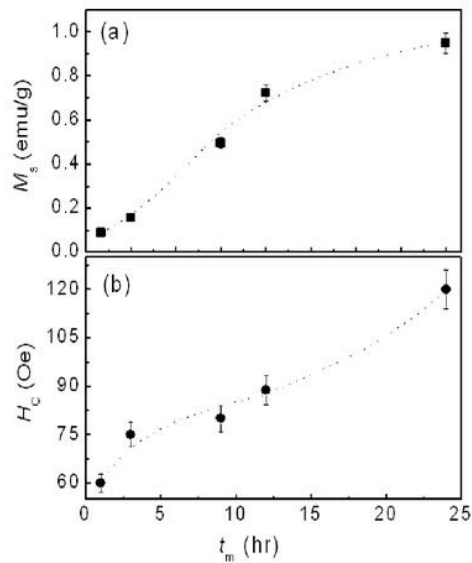

**Figure 7.** Dependences of (a)  $M_s$  and (b)  $H_c$  on  $t_m$  for the nanocrystalline ZnO samples (dotted lines are to guide the eye only).

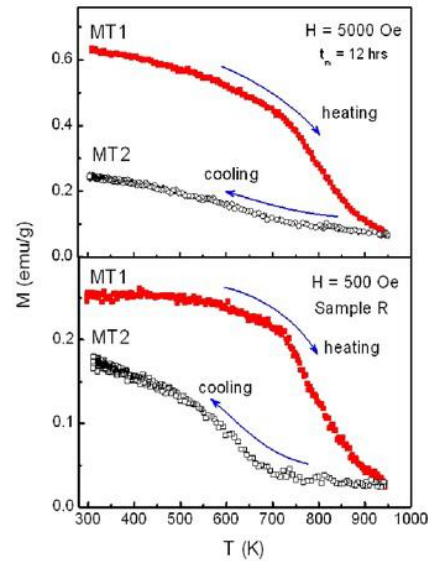

**Figure 8.** Temperature dependences of magnetization for the samples  $t_m = 12$  hrs and R measured under the heating (MT1) and cooling (MT2) conditions.

The crystallization of metastable nanoparticles leads to the separation of these two curves. The variation tendency of the  $M$ - $H$  curves for the samples is very similar. This reflects the samples having the same ferromagnetic nature/origin. Concerning the heating process MT1, the ferromagnetic-paramagnetic (FM-PM) phase transition takes place at  $T_{C1} \approx 850$  K. In contrast, the measurement according to the cooling process MT2 introduces the FM-PM phase transition at  $T_{C2} \approx 600$  K. The separation between two curves MT1 and MT2 is about 0.4 emu/g for the  $t_m = 12$  hrs sample, and 0.1 for sample R. Such the features indicate that the nanocrystalline samples are metastable. If we re-measure  $M$ - $T$  on these samples following the heating direction once again, the curves recorded will coincides with their MT2 curves.

The above phenomena can be explained as follows: the nanocrystalline samples after ball milling usually contain a high density of lattice defects and grain boundaries. The binding between atoms located at gain boundaries and surfaces is thus weak, which is broken easily by thermal energy due to the heating from 300 to 950 K as measuring MT1. As a result, weakly bound atoms can be evaporated, and the quality of nanoparticles will be improved remarkably, because of defect annihilation and structural reorganization [17]. When the samples are cooled down from 950 K to measure MT2, the crystallization in nanoparticles takes place. There is a transformation from the



metastable state to the stable state, and the crystallite size can be also increased. Another possibility is that the heating at high temperatures can also causes changes in the composition of ZnO nanoparticles and the secondary phase  $\text{Fe}_{0.902}\text{O}$ ; *i.e.*, Fe can diffuse into ZnO crystals, and in contrast Zn can diffuse into  $\text{Fe}_{0.902}\text{O}$ . Such the circumstances lead to a difference between two curves MT1 and MT2, as can be seen in Figure 8. Regarding to a question of the nature of the ferromagnetism, we have paid attention to the XRD and EDX data. To the limit of the experimental tools, only three elements of Zn, O and Fe are found in our samples corresponding to structural phases of ZnO and  $\text{Fe}_{0.902}\text{O}$ . Among these,  $\text{Zn}^{2+}$  and  $\text{O}^{2-}$  are nonmagnetic ions, and commercial ZnO powders is known as a diamagnetic material [19, 24].

Recently, Sanyal *et al.* [19] have reported that ZnO nanoparticles fabricated by mechanical milling also exhibits diamagnetic behavior. For the case of the ferromagnetism in ZnO materials caused by lattice defects,  $M_s$  values are usually very small, in the range of  $1 \times 10^{-5}$  -  $1 \times 10^{-2}$  emu/g [24-27]. Meanwhile, large values of  $M_s \approx 0.1$  -  $1.0$  emu/g are gained from our samples, see Figs. 7 and 8. With these results, the ferromagnetism in our samples is definitely generated from a Fe-related secondary phase. Having compared to the magnetic behavior of iron and iron oxides shown in Table 1, compounds Fe, FeO,  $\text{Fe}_2\text{O}_3$ ,  $\text{ZnFe}_2\text{O}_4$  (both normal and inverse spinel structures), and  $(\text{Zn, Fe})_3\text{O}_4$  can not be responsible for the ferromagnetism because their magnetic phase transition temperature (the Curie temperature or the Néel temperature) is far from that of our samples.

There is only  $\text{Fe}_3\text{O}_4$  with  $T_C \approx 858$  K very close to the value  $T_C \approx 850$  K of our nanoparticles. However, the XRD data in Figure 3 do not indicate its existence. We believe that the ferromagnetism

**Table 1. Magnetic properties of some secondary phases related to iron and iron oxides.**

Phase	Magnetic nature	Curie temperature or Néel temperature (K)	Reference
$\text{Fe}_{0.902}\text{O}$ (nanocrystalline, cubic)	Ferromagnetic	$\sim 850$	Present work
Fe	Ferromagnetic	1043	[28]
FeO (cubic)	Antiferromagnetic	198	[28]
$\text{Fe}_2\text{O}_3$	Ferromagnetic	948	[29]
$\text{Fe}_3\text{O}_4$	Ferromagnetic	858	[28]
$(\text{Zn, Fe})_3\text{O}_4$	Ferromagnetic	440	[23]
$\text{ZnFe}_2\text{O}_4$ (bulk, normal spinel)	Nonmagnetic	-	[23]
$\text{ZnFe}_2\text{O}_4$ (nanocrystalline, inverse spinel)	Ferrimagnetic	-	[23]



in the samples is caused by wuestite  $\text{Fe}_{0.902}\text{O}$ . It also appears in nanosizes and is metastable, similar to ZnO nanoparticles. The enhancement in ferromagnetic order is a consequence of development of this phase when  $t_m$  is increased. For sample R, nanoparticles cling directly to the milling media for a long time, the magnetization is thus highest.

## CONCLUSION

We used the mechanical milling to prepare ZnO nanoparticles, started from commercial ZnO powders. The variation of the milling time  $t_m$  from 1 to 24 hrs reduced the crystallite size  $D$  to about 13.5 nm. The EDX and XRD studies revealed the presence of Fe impurity generated from the grinding vial wall and balls. Under high energy of the milling operation this impurity constituted  $\text{Fe}_{0.902}\text{O}$  with the wuestite-type structure, which was responsible to the high-temperature ferromagnetism in ZnO nanoparticles. The  $t_m$  increase would enhance the impurity level, and thus resulted in the increase in the ferromagnetic order. Notably, ZnO nanoparticles prepared by the mechanical milling are metastable, and there is the crystallization when they are cooled from high temperatures.

## REFERENCES

- Arora, A., P. J. George, A. Arora, V. K. Dwivedi and V. Gupta. *Sensors & Transducers Journal* 91 (2008): 70.
- Jagadish, C., and S. J. Pearton. "Zinc oxide bulk." *Thin Films and Nanostructures*, Elsevier, 2006.
- Wang, Z. I. *Journal of Physics: Condensed Matter* 16 (2004): R828.
- Liao, L., H. B. Lu, M. Shuai, J. C. Li, Y. L. Liu, C. Liu, Z. X. Shen and T. Yu. *Nanotechnology* 19 (2008): 175501.
- Qin, Y., X. D. Wang and Z. L. Wang. *Nature* 451 (2008): 809.
- Wang, Z. I. and J. H. Song. *Science* 312 (2006): 242.
- Xiang, B., P. W. Wang, X. Z. Zhang, S. A. Dayeh, D. P. R. Aplin, C. Soci, D. P. Yu and D. L. Wang. *Nano Letter* 7 (2007): 323.
- Yuan, G. D., W. J. Zhang, J. S. Jie, X. Fan, J. A. Zapien, Y. H. Leung, L. B. Luo, P. F. Wang, C. Lee, S., and S. T. Lee. *Nano Letter* 8 (2008): 2591.
- Brayner, R., S. A. Dahoumane, C. Yepremian, C. Djediat, M. Meyer, A. Coute and F. Fievet. *Langmuir* 26 (2010): 6522.
- Chu, D. W., Y. Masuda, T. Ohji and K. Kato. *Langmuir* 26 (2010): 2811.
- N. Padmavathy, N., and R. Vijayaraghavan. *Science and Technology Advanced Materials* 9 (2008): 035004.
- Kathirvelu, S., D. S. Louis and B. Dhurai. *Indian Journal of Fibre and Textile Research* 34 (2009): 267.

13. Suryanarayana, C. *Progress in Materials Science* 46 (2001): 1.
14. Bégin-Colin, S., T. Giroit, G. Le Caër and A. Mocellin. *Journal of Solid State Chemistry* 149 (2000): 41.
15. Damonte, L.C., L. A. Mendoza Zélis, B. Mari Soucase and M. A. Hernández Fenollosa. *Powder Technology* 148 (2004): 15.
16. Dutta, S., S. Chattopadhyay, M. Sutradhar, A. Sarkar, M. Chakrabarti, D. Sanyal and D. Jana. *Journal of Physics: Condensed Matter* 19 (2007): 236218.
17. Glushenkov, A.M., H. Z. Zhang, J. Zou, G. Q. Lu and Y. Chen. *Nanotechnology* 18 (2007): 175604.
18. Lemine, O.M., A. Alyamani and M. Bououdina. *International Journal of Nanotechnology and Applications* 2 (2008): 161.
19. Sanyal, D., T. K. Roy, M. Chakrabarti, S. Dechoudhury, D. Bhowmick and A. Chakrabarti. *Journal of Physics: Condensed Matter* 20 (2008): 045217.
20. Vojisavljevic, K., M. Scepanovic, T. Sreckovic, M. Grujic-Brojein, Z. Brankovic and G. Brankovic. *Journal of Physics: Condensed Matter* 20 (2008): 475202.
21. Sreckovic, T., S. Bernik, M. Ceh and K. Vojisavljevic. *Journal of Microscopy* 232 (2008): 639.
22. Warren, B.E. *X-ray diffraction: Reading, MA: Addison-Wesley*, 1969.
23. Morkoc, H., and U. Ozgur. "Zinc Oxide: Fundamentals." *Materials and Device Technology*, Weinheim: WILEY-VCH Verlag GmbH & Co. KGaA, 2009.
24. Hong, N.H. *Magnetism in Semiconducting Oxides*, Transworld Research Network, 2007.
25. Phan, T.L., and S. C. Yu. *Journal of the Korean Physical Society* 56 (2010): 1160.
26. Sundaresan, A., R. Bhargavi, N. Rangarajan, U. Siddesh and C. N. R. Rao. *Review B* 74 (2006): 161306.
27. Straumal, B.B., A. A. Mazilkin, S. G. Protasova, A. A. Myatiev, P. B. Straumal, G. Schütz, P. A. van Aken, E. Goering and B. Baretzky. *Physical Review B* 79 (2009): 205206.
28. Kittel, C. *Introduction to Solid State Physics*, John Willey & Sons, 2005.
29. Lowrie, W. *Fundamentals of Geophysics*, Cambridge: Cambridge University Press, 1997.

### DAFTAR MITRA BESTARI

Mitra Bestari yang telah berpartisipasi untuk Jurnal Fisika – Himpunan Fisika Indonesia pada penerbitan Volume 10 - Nomor 2 - Desember 2010 adalah:

No	Nama
1.	<sup>24</sup> Prof. Surian Pinem, M.Si. Pusat Teknologi Reaktor dan Keselamatan Nuklir, Badan Tenaga Nuklir Nasional (PTRKN-BATAN) Kawasan Puspiptek Serpong 15314 Tangerang Selatan.
2.	Dr. Tech. Djoko Triyono. Jurusan Fisika <sup>51</sup> Fakultas Matematika dan Ilmu Pengetahuan Alam Universitas Indonesia Depok 16424.
3.	<sup>4</sup> Ir. Harry R. Arjadi, M.Sc. Pusat Penelitian Sistem Mutu dan Teknologi Pengujian - Lembaga Ilmu Pengetahuan Indonesia (P2SMTP-LIPI) Kawasan Puspiptek Serpong 15314 Tangerang Selatan.
4.	<sup>33</sup> Buldan Muslim, M.Si. Lembaga Penerbangan dan Antariksa Nasional (LAPAN) Jl. Dr. Junjunan 133 Bandung 40173.

Segecap Dewan Editor dan Editor Pelaksana Jurnal Fisika – HFI mengucapkan <sup>37</sup> terima kasih dan penghargaan yang setinggi-tingginya atas partisipasi Mitra Bestari dan berharap agar kerjasama ini dapat terus berlanjut.

---

## INDEKS KATA KUNCI

Arang, 122  
*Combustion Characteristics*, 116  
Data *logger*, 83  
Gelombang Kelvin, 71  
Karbon, 122  
Konduktivitas listrik, 122  
*Magnetic entropy*, 95  
*Magnetism*, 105  
*Magnetotransport property*, 95  
*Mechanical Milling*, 105  
Mikrokontroler Atmega32, 83  
*OH radical*, 116  
Pergeseran tanah, 83  
Periodisitas, 71  
*Perovskite manganites*, 95  
Propagasi, 71  
Suhu karbonisasi, 122  
*Vegetable Oil*, 116  
*X-ray diffraction*, 105  
*ZnO Nanoparticles*, 105



---

**INDEKS PENULIS**

Achmad Subhan, 122  
Andi Setiono, 83  
Andi Suhandi, 122  
Bambang Widiyatmoko, 83  
D. H. Manh, 105  
Fredina Destyorini, 122  
K. Tarigan, 95, 105  
Kuniyuki Kitagawa, 116  
M. Ginting, 95, 105  
N. A. Tuan, 95  
N. H. Sinh, 95  
Nanik Indayaningsih, 122  
Nelfa Desmira, 116  
Noriaki Matsui, 116  
P. Q. Thanh, 95  
Prabowo Puranto, 83  
Sandro Wellyanto Lubis, 71  
Sonni Setiawan, 71  
T. D. Thanh, 105  
T. L. Phan, 95, 105  
V. D. Lam, 105  
V. V. Khai, 95

# INFLUENCE OF MILLING TIME ON STRUCTURAL AND MAGNETIC PROPERTIES OF ZnO NANOPARTICLES PREPARED BY MECHANICAL MILLING

## ORIGINALITY REPORT

19%

SIMILARITY INDEX

14%

INTERNET SOURCES

16%

PUBLICATIONS

%

STUDENT PAPERS

## PRIMARY SOURCES

1

Oudhia, A., A. Choudhary, S. Sharma, S. Aggrawal, and S.J. Dhoble. "Study of defect generated visible photoluminescence in zinc oxide nano-particles prepared using PVA templates", Journal of Luminescence, 2014.

Publication

1%

2

Mera, J.. "On the structural analysis and magnetic behavior of heavily doped Zn<sup>1+</sup>-xMn<sup>x</sup>O nanopowders synthesized by wet chemistry method", Journal of Magnetism and Magnetic Materials, 201205

Publication

1%

3

Azzaza, Sonia, Safia Alleg, and Joan-Josep Suñol. "Microstructure characterization and thermal stability of the ball milled iron powders", Journal of Thermal Analysis and Calorimetry, 2015.

Publication

1%

4

Internet Source

1 %

5

Nasution, Aulia, Dwi Bayuwati, Tomi B. Waluyo, and Bambang Widiyatmoko. "Preliminary design of land displacement-optical fiber sensor and analysis of observation during laboratory and field test", International Seminar on Photonics Optics and Its Applications (ISPhOA 2014), 2015.

Publication

1 %

6

Rezaee, M.. "Application of statistical methodology for the evaluation of mechanically activated phase transformation in nanocrystalline TiO<sub>2</sub>", Journal of Alloys and Compounds, 20110908

Publication

&lt;1 %

7

Zang, C.H.. "Growth and optical properties of ZnO microwells by chemical vapor deposition method", Physica B: Physics of Condensed Matter, 20090228

Publication

&lt;1 %

8

[www.jti.lipi.go.id](http://www.jti.lipi.go.id)

Internet Source

&lt;1 %

9

The-Long Phan, P. Zhang, D. S. Yang, T. D. Thanh, D. A. Tuan, S. C. Yu. " Origin of ferromagnetism in BaTiO nanoparticles prepared by mechanical milling ", Journal of

&lt;1 %

10

[edoc.site](http://edoc.site)

Internet Source

<1 %

11

A M Glushenkov. "Efficient production of ZnO nanowires by a ball milling and annealing method", Nanotechnology, 05/02/2007

Publication

<1 %

12

Tapatee Kundu Roy, D. Sanyal, Debasis Bhowmick, Alok Chakrabarti. "Temperature dependent resistivity study on zinc oxide and the role of defects", Materials Science in Semiconductor Processing, 2013

Publication

<1 %

13

Al-Hartomy, O. A., F. Al-Solamy, A. A. Al-Ghamdi, M. A. Ibrahim, N. Dishovsky, and F. El-Tantawy. "Pressure Sensors Based on Polyvinyl Chloride/Graphite/Nickel Nanocomposites", Journal of Elastomers and Plastics, 2011.

Publication

<1 %

14

[www.orientjchem.org](http://www.orientjchem.org)

Internet Source

<1 %

15

[www.rsphysse.anu.edu.au](http://www.rsphysse.anu.edu.au)

Internet Source

<1 %

16

[repository.unair.ac.id](http://repository.unair.ac.id)

Internet Source

<1 %



17

[www.fascicula9.ugal.ro](http://www.fascicula9.ugal.ro)

Internet Source

&lt;1 %

18

Han, Han, Enhong Sheng, Yonghong Ni, Yue Ma, Nannan Xiang, and Xiang Ma. "Sheet-tube-rod transformation for ZnO nanorods prepared by a simple reflux route", Materials Research Bulletin, 2016.

Publication

&lt;1 %

19

Zheng, X.. "Simple synthesis of one-dimensional copper chalcogenides and its reducing and self-sacrificing templates for Au nanowires", Materials Chemistry & Physics, 20081115

Publication

&lt;1 %

20

D. Sanyal, Mahuya Chakrabarti, A. Chakrabarti. "Synthesis and positron characterizations of ferromagnetic and paramagnetic samples", Solid State Communications, 2010

Publication

&lt;1 %

21

[diposit.ub.edu](http://diposit.ub.edu)

Internet Source

&lt;1 %

22

Zhang, T.. "The easy formation of the monoclinic MCE phase in  $Gd_5Si_2Ge_2$  with the addition of Sn", Materials Characterization, 200810

Publication

&lt;1 %

23	<a href="http://www.transeem.org">www.transeem.org</a> Internet Source	<1 %
24	<a href="http://jurnal.batan.go.id">jurnal.batan.go.id</a> Internet Source	<1 %
25	<a href="http://xxx.lanl.gov">xxx.lanl.gov</a> Internet Source	<1 %
26	<a href="http://bmr.lbl.gov">bmr.lbl.gov</a> Internet Source	<1 %
27	<a href="http://iwamsn.ac.vn">iwamsn.ac.vn</a> Internet Source	<1 %
28	<a href="http://repo-nkm.batan.go.id">repo-nkm.batan.go.id</a> Internet Source	<1 %
29	<a href="http://www.idosi.org">www.idosi.org</a> Internet Source	<1 %
30	Zhang, Yue, Yousong Gu, Yunhua Huang, Xiaogin Yan, and Qingliang Liao. "PIEZOTRONIC VIBRATION DETECTOR BASED ON ZNO NANOWIRE ARRAYS", Controllable Synthesis Structure and Property Modulation and Device Application of One-Dimensional Nanomaterials, 2012. Publication	<1 %
31	Morko. "ZnO-Based Dilute Magnetic Semiconductors", Zinc Oxide, 01/14/2009 Publication	<1 %

32 Yongliang Chen, Suhua Yang, Mingchao Li, Yun Zhang, Yajing Cui, Cuihua Cheng, Xifeng Pan, Guo Yan, Yong Feng, Yong Zhao. " Ag Doping Effect on the Superconductivity of Nb Al Prepared Using High-Energy Ball Milling Method ", IEEE Transactions on Applied Superconductivity, 2019

Publication

<1 %

---

33 [www.apn-gcr.org](http://www.apn-gcr.org)

Internet Source

<1 %

---

34 V. A. Karpina, V. I. Lazorenko, C. V. Lashkarev, V. D. Dobrowolski et al. "Zinc oxide - analogue of GaN with new perspective possibilities", Crystal Research and Technology, 2004

Publication

<1 %

---

35 Huang, Yunfang, Yuelin Wei, Jihuai Wu, Chongshen Guo, Ming Wang, Shu Yin, and Tsugio Sato. "Low temperature synthesis and photocatalytic properties of highly oriented ZnO/TiO<sub>2</sub>-xNy coupled photocatalysts", Applied Catalysis B Environmental, 2012.

Publication

<1 %

---

36 Arora, A.. "Zinc oxide thin film-based MEMS acoustic sensor with tunnel for pressure compensation", Sensors & Actuators: A. Physical, 20080215

Publication

<1 %

---

37	<a href="http://korem101antasari.mil.id">korem101antasari.mil.id</a> Internet Source	<1 %
38	<a href="http://www.sciepub.com">www.sciepub.com</a> Internet Source	<1 %
39	<a href="http://www.em-consulte.com">www.em-consulte.com</a> Internet Source	<1 %
40	<a href="http://ictmumbai.edu.in">ictmumbai.edu.in</a> Internet Source	<1 %
41	<a href="http://digilib.k.utb.cz">digilib.k.utb.cz</a> Internet Source	<1 %
42	<a href="http://nanoscalereslett.springeropen.com">nanoscalereslett.springeropen.com</a> Internet Source	<1 %
43	<a href="http://www.diva-portal.org">www.diva-portal.org</a> Internet Source	<1 %
44	Y.H. Leung, A.B. Djuriscic, M.H. Xie. "Simple Fabrication Method for ZnO Nanoneedle Structures", Conference on Optoelectronic and Microelectronic Materials and Devices, 2004., 2004 Publication	<1 %
45	X. Zhang. "Evidence for high- $T_{\{c\}}$ ferromagnetism in $Zn_{\{x\}}(ZnO)_{\{1-x\}}$ granular films mediated by native point defects", Physical Review B, 11/2009 Publication	<1 %



46

[www.mrs.org](http://www.mrs.org)

Internet Source

&lt;1 %

47

Kim, Ki-Joong, Peter B. Kreider, Changho Choi, Chih-Hung Chang, and Ho-Geun Ahn. "Visible-light-sensitive Na-doped p-type flower-like ZnO photocatalysts synthesized via a continuous flow microreactor", RSC Advances, 2013.

Publication

&lt;1 %

48

Phan, The-Long, Y. D. Zhang, D. S. Yang, N. X. Nghia, T. D. Thanh, and S. C. Yu. "Defect-induced ferromagnetism in ZnO nanoparticles prepared by mechanical milling", Applied Physics Letters, 2013.

Publication

&lt;1 %

49

[iopscience.iop.org](http://iopscience.iop.org)

Internet Source

&lt;1 %

50

[lipi.go.id](http://lipi.go.id)

Internet Source

&lt;1 %

51

[www.scribd.com](http://www.scribd.com)

Internet Source

&lt;1 %

52

Amirkhanlou, Sajjad, Mostafa Ketabchi, and Nader Parvin. "Nanocrystalline/nanoparticle ZnO synthesized by high energy ball milling process", Materials Letters, 2012.

Publication

&lt;1 %

Prem Ranjan, Raj Kamal Singh, H. Suematsu,

53	Ligy Phillip, R. Sarathi. "Synthesis of nano-ZnO by wire explosion process and its photocatalytic activity", Journal of Environmental Chemical Engineering, 2017 Publication	<1 %
54	Karmakar, R., S.K. Neogi, Aritra Banerjee, and S. Bandyopadhyay. "Structural; morphological; optical and magnetic properties of Mn doped ferromagnetic ZnO thin film", Applied Surface Science, 2012. Publication	<1 %
55	Wang, N.. "Growth of nanowires", Materials Science & Engineering R, 20080331 Publication	<1 %
56	<a href="http://repositorium.sdum.uminho.pt">repositorium.sdum.uminho.pt</a> Internet Source	<1 %
57	<a href="http://journal.unnes.ac.id">journal.unnes.ac.id</a> Internet Source	<1 %
58	Chakrabarti, Mahuya, D. Jana, and D. Sanyal. "Positron annihilation characterization of nanocrystalline ZnO", Vacuum, 2013. Publication	<1 %
59	Sherif El-Eskandarany, M.. "Mechanical solid-state reduction of haematite with magnesium", Journal of Alloys and Compounds, 20010116 Publication	<1 %

Michael Hitchcock. "The Bimanese kris;  
Aesthetics and social value", *Bijdragen tot de  
taal-, land- en volkenkunde / Journal of the  
Humanities and Social Sciences of Southeast  
Asia*, 1987

Publication

---

<1%

---

Exclude quotes Off

Exclude matches Off

Exclude bibliography Off